

# Laboratory Investigation on Rheological Characteristics of Asphalt Mastic with Waste Powder Materials from Mosaic Tiles as Sustainable Filler

**A.I. Al-Hadidy\***  
[alhadidy@uomosul.edu.iq](mailto:alhadidy@uomosul.edu.iq)

**Mohammed Ghanim Jamel\***  
[mohammed\\_g72@uomosul.edu.iq](mailto:mohammed_g72@uomosul.edu.iq)

**Tan Yi-qiu\*\***  
[tanyiqiu@163.com](mailto:tanyiqiu@163.com)

**Dong Zejiao\*\***  
[hitdji@hit.edu.cn](mailto:hitdji@hit.edu.cn)

**Wang Jia-ni\*\***  
[wangjiani@hit.edu.cn](mailto:wangjiani@hit.edu.cn)

\*Civil Engineering Department, College of Engineering, University of Mosul, Mosul, Iraq

\*\* School of Transportation Science and Engineering, (HIT), China.

Received: 2023-01-12

Received in revised form: 2023-02-16

Accepted: 2023-02-26

## ABSTRACT

To evaluate the possibility of using waste powder material (WPM) produced from mosaic tiles polishing as a sustainable filler in asphalt mixture, some properties of asphalt mastic containing WPM were investigated in this paper, compared with the common limestone mineral (LSM) filler. The investigated mastic consisted of asphalt and filler at a mass ratio of 1:1. The rheological properties were tested using the penetration, softening point, ductility, elastic recovery, Furol viscosity, extensional viscosity, Dynamic Shear Rheometer, temperature susceptibility, compatibility, and Cone penetration tests. Results indicate the possibility of WPM as sustainable filler derived from mosaic tile polishing facilities to improve the performance of asphalt. The WPM has better effect on improving the shear, rutting and fatigue resistance as well as temperature sensitivity of asphalt mastic than LSM.

## Keywords:

Rheological characteristics; Waste powder materials; Limestone filler.

This is an open access article under the CC BY 4.0 license (<http://creativecommons.org/licenses/by/4.0/>).  
<https://rengj.mosuljournals.com>

## 1. INTRODUCTION

Economic and industrial development will continue to produce growing volumes of waste as the global population rises. Any type of disposal strategy directly affects the delicate balance of the physical, chemical, and biological environments that make up our planet's biosphere [1]. For a variety of reasons, the use of waste materials in construction as a partial or full substitute for virgin materials has increased (including economics). In general, it has been discovered that the use of some waste materials, such as fiber, polyethylene, sulfur waste, crumb rubber, reclaimed asphalt pavement, recycled waste lime, polypropylene, recycled red brick powder, residual volcanic ash, carbon black, fly ash, and charcoal, is cost-efficient, responsible for the environment, and effective in enhancing some of the performance aspects of asphalt mixes [2, 3]. Studies [4-6] on the subject of using plastic in roads have discovered appreciable

enhancements in the tensile strength, resistance to moisture, resistance to cracking, and durability of asphalt binder and mixtures.

When activated charcoal is used as an inorganic mastic filler with asphalt [7], concluded that it performs better than limestone mineral filler in terms of temperature sensitivity and shear strength. Furthermore, activated charcoal has a favorable effect on the asphalt mastic's high-temperature qualities while having a mixed effect on its low-temperature aspects. The obtained results further demonstrate that physical adsorption between the charcoal as mastic filler and asphalt cement is the primary mode of interaction.

Millions of tons of waste powder materials (WPM) are produced annually by Iraqi mosaic tile manufacturing companies and thrown in landfills. These accumulated wastes can provide good strength, improved abrasion resistance,

resistance to rot, mildew, and many substances that might cause degradation. These wastes are excellent choices for a range of civil engineering uses, including the creation and maintenance of pavement [2].

A firm in Iraq is producing more WPM, which is challenging for waste management and polluting the environment [8]. Reusing the waste is the most environmentally beneficial way to handle the problem of getting rid of bulk rubbish. The considerable use of composite materials in Iraq for the construction and upkeep of road surfaces creates a sizable opportunity for waste-material recycling. The safe disposal of bulk waste is important, but it's also important to minimize the negative environmental effects that the use of fillers in paving construction industry has on the environment [9].

The greatest way to lower those energy and emission levels is to increase ongoing efforts to lessen the quantity of filler required. This can be done mostly by lowering or eliminating the amount of popular fillers in asphalt mixtures, such as calcium carbonate, and by increasing the lifespan of asphalt mixtures [9].

Like the vast majority of solid waste put in landfills, WPM does not decompose. Between 10 and 20 million tons of WPM are reportedly generated and dumped in Iraq each year. WPM costs landfills about \$105 every ton. As a result, the cost of landfilled areas varies annually, from 665 to 2000 000 USD [8]. In order to cut costs and environmental damage, WPM is projected to become a preferred mineral filler for asphalt. WPM is an attractive choice that also seems to improve the qualities of paving concrete mixtures [2] since it is more economical (on the order of 0.25 USD/kg, respectively) when compared to other fillers, such as calcium carbonate.

Only a few studies [2, 9, 10]. were conducted during the past ten years on the use of some of these wastes as a filler or polymer fiber in bitumen mixtures. The outcomes from incorporating garbage in asphalt mixtures are significant and encouraging, according to these investigations. On the other hand, no research has been done on the use of WPM as a filler in asphalt paving mixtures. When replacing or adding any waste materials to bitumen mixtures, three key considerations should be made [11]. To start, annually cost evaluations should be carried out to ascertain each material's efficacy. The impact of the asphalt on the caliber and effectiveness of the pavement is a second factor to take into account. Incorporating garbage that significantly raises the price of the pavement while also reducing its useful life or raising the cost of maintenance would be

poor economics. Utilizing waste materials also takes into account the benefits to the environment of their disposal in landfills.

The huge potential for WPM recovery and encapsulation is demonstrated by these data. Bituminous road surfaces are a fantastic method to add a lot of distinctive WPM to a pavement design whilst also enhancing the durability and strength of the pavement courses. The new research is anticipated to help improve our knowledge of how paving mixes including WPM perform for the long-duration construction of roads. To the authors' knowledge, no research has been done on employing WPM as a mineral filler in asphalt mixtures. There is still a need for more research on this subject, thus that is what has been done.

## 2. OBJECTIVES OF THE RESEARCH

The major goal of the current experiment was to examine the qualities of WPM and asphalt mastic that contain WPM in relation to one another.

Many tests including penetration, softening point, ductility, elastic recovery, Furol viscosity, extensional viscosity, Dynamic Shear Rheometer, temperature susceptibility, compatibility, and Cone penetration were applied to evaluate the related properties of asphalt mastic with WPM and the feasibility of WPM as sustainable filler in asphalt pavement compared with conventional lime stone filler (LSF).

## 3. TESTS PROCEDURES

### 3.1. Base asphalt, WPM and LSM

Asphalt utilized in this research was 40-50 (A40) penetration grade and its physicochemical characteristics were tabulated in Table 1. The results indicated that A40 satisfy ASTM [12] and SCRIB [13] specifications for penetration graded asphalt.

Table 1: Properties of base asphalt

Characteristics	Value	SCRIB [13]	ASTM [12]
Penetration (25°C, 100g, 5s, dmm)	44	40-50	40-50
Softening point, °C	51.3	-	50-58
Ductility((25°C, 5 cm/min, cm)	150*	>100	>100
Elastic recovery (25 °C, 50 mm/min, cm ), %	65	-	-
Flash point (COC, °C)	277	>232	>240
Loss on heat (5hrs, 163 °C, %)	0.12	0.75 max.	0.2 max
P.I.	-1.668	-	-2 to +2
Retained Penetration % of original (25 deg. C, 100gm, 5 s, 0.1mm)	61	55 min.	-
Residue Ductility (25 °C, 50 mm/min, cm)	55	75min.	-

Waste powder materials (WPM) are chosen as filler for the asphalt mixture. WPM, a byproduct of mosaic tile polishing factories, is piling up in Nineveh province, Iraq. WPM is collected and dried to a constant weight in a 105 °C oven, and then fragmented by a jaw crusher to achieve the same percentage passing as LSM. In Table 2, the physico-chemical and gradational characteristics of WPM materials are displayed.

Table 2: Physicochemical properties of LSM and WPM

Test property	Value (wt. %)		
	LSM	WPM	
Silicon Dioxide (SiO <sub>2</sub> )	22.23	22.19	
Aluminum Oxide (Al <sub>2</sub> O <sub>3</sub> )	6.18	3.95	
Ferric Oxide (Fe <sub>2</sub> O <sub>3</sub> )	3.27	0.205	
Calcium Oxide (CaO)	61.3	66.67	
Magnesium Oxide (MgO)	3.9	0.68	
Potassium Oxide (K <sub>2</sub> O)	0.16	0.42	
Sulfur Trioxide (SO <sub>3</sub> )	2.13	2.73	
Sodium Oxide (Na <sub>2</sub> O)	---	0.064	
Specific gravity	2.734	2.808	
Gradation			
Sieve size (mm)	Passing (%)		NCCL [14]
	CaCO <sub>3</sub>	WPM	
0.6	100	100	100
0.3	100	100	95-100
0.075	98	94	70-100
Plasticity index	1.2	2	Max. 4%

### 3.2. Asphalt mastic production

For the production of asphalt mastic, each of WPM and LSM were mixed with A40 at a mass ratio of 1:1 under (155±5°C, 500 rpm, and 3±1 minutes) conditions to obtain a homogeneous mastic.

### 3.3. Testing rheological and mechanical characteristics of WMA binders

The rheological and mechanical tests conducted on WPM and LSM mastics as per ASTM [14] include: penetration (D-5), softening point (D-36), ductility (D-113), elastic recovery (D-3633M), Furol viscosity (D-88), extensional viscosity, Dynamic Shear Rheometer (D-7175), temperature susceptibility, compatibility, and Cone penetration.

## 4. RESULTS AND DISCUSSIONS

### 4.1. Penetration and softening point

Penetration and softening point of WPM and LSM mastics were examined and the results are depicted in Figure 1 and 2. The results notify that WPM are effective in improving A40 characteristics. Penetration at 25°C, for WPM and LSM were found to be 40 and 42, respectively. From these results, it can be notified that WPM

well done against shear resistance in moderate to high temperatures than other LSM. As compared with A40, the percent decrease in penetration of WPM and LSM at 25°C was noticed to be 9.0%, and 4.6%, respectively. When it comes to penetration, the averages of the WPM and LSM mastics (i.e., they all show approximately similar penetration) were significant.

The softening point, R&B traditional test was utilized to examine the high-temperature rutting characteristics of WPM and LSM mastics. From Figure 2, R&B for WPM and LSM were noticed to be 61 and 57°C, respectively. It is shown that WPM mastic exhibited R&B higher than LSM. WPM and LSM exhibited 19% and 11.2% higher R&B than A40 (i.e. WPM more resistance against rutting than LSM). This is because that WPM contains higher amount of Calcium Oxide (CaO) in its chemical composition than LSM.

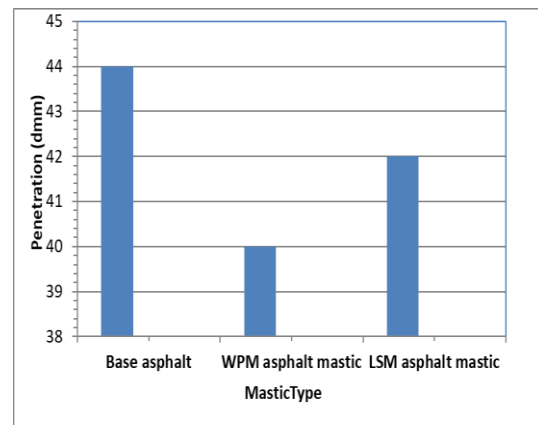


Fig. 1 Penetration of asphalt mastic

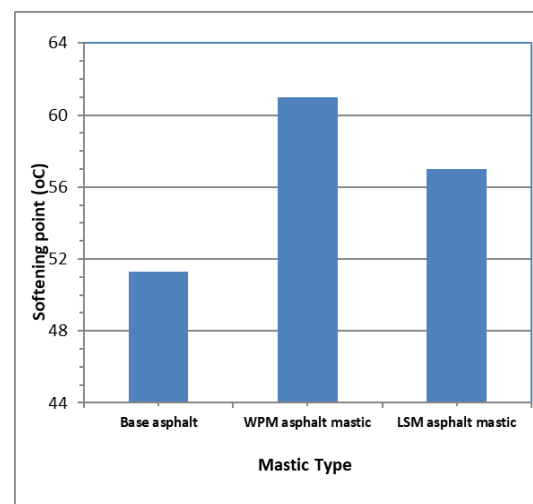


Fig. 2 Softening point of asphalt mastic

#### 4.2. Ductility and elastic recovery

The ductility (Du) and elastic recovery (Er) test was performed to examine the elasticity characteristics of WPM and LSM mastics. Figure 3 shows Du at 25°C for WPM and LSM mastics. Testing Figure 3, it can be noticed that WPM and LSM mastics having Du values of 95 and 101 cm at 25°C, respectively. WPM has a ductility value slightly lower than LSM and at the same time lower than the minimum limit of ASTM [12] and SCRB [13] requirements of 100+cm. This is because that LSM is finer than WPM as indicated in Table 3. However, WPM mastic provides adequate adhesive property and thus adequate behavior in the field.

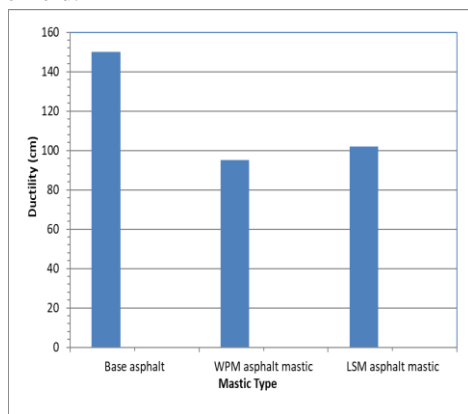


Fig. 3 Ductility of asphalt mastic

Similarly, Er percentage at 25°C for WPM and LSM mastics were found to be 79.6% and 82%, respectively. Testing Figure 4, it can be notified that no significant difference in Er values at 25°C. These results notify that WPM and LSM have the same elasticity value at medium temperatures (i.e., WPM and LSM give similar tensile strain of asphalt-mix layer in flexible pavement).

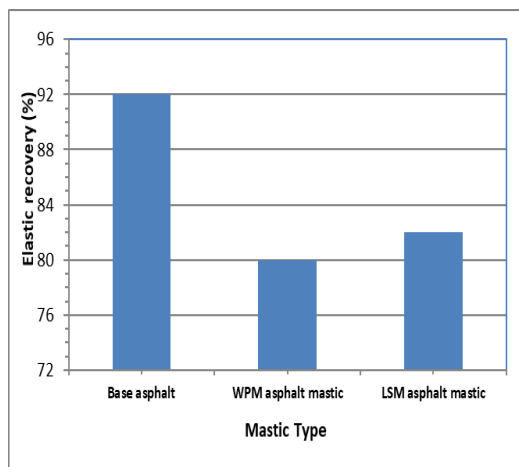


Fig. 4 Elastic recovery of asphalt mastic

#### 4.3. Furol viscosity

To determine the mixing and compaction temperatures of WPM and LSM mastics, the furol viscosity (FV) of the two materials was measured using a Saybolt-Furol viscometer at various temperatures. According to the Asphalt Institute manual, these temperatures result in Saybolt-Furol viscosities of 85 and 140 s, respectively. Figure 5 depicts the FV. It was notified that WPM and LSM having mixing temperatures values of 163 and 162°C, respectively. Similarly, the compaction temperatures for these mastics were found to be 156 and 155°C, respectively. From these, it can be concluded that the viscosity of WPM binder is similar to that of LSM.

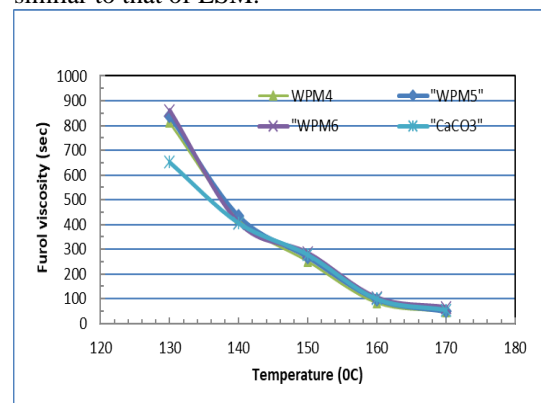


Fig. 5 Furol viscosity of asphalt mastic

#### 4.4. Dynamic Shear Rheometer test (DSR)

The main technique for figuring out a material's viscoelasticity is rheological measurement. The dynamic shear rheometer (DSR) test was used in this study to determine the asphalt binder's shear modulus and phase angle. The rheological characteristics and rutting resistance of asphalt mastic were assessed at 76°C in accordance with ASTM D7175 [15]. An asphalt film sample with dimensions of 25 mm in diameter and 2 mm in thickness was sandwiched in this experiment between a fixed steel plate and an oscillating plate with a 10 rad/s angular frequency while being subjected to a constant torque. The rutting ( $G^*/\sin \delta$ ) and fatigue ( $G^*\sin \delta$ ) resistance parameters were determined as shown in Figures 6 and 7. These figures indicate that WPM asphalt mastic is more resistant to rutting (i.e. smaller amount of deformation of asphalt materials or shorter loading time) and fatigue at high temperatures than LSM asphalt mastic, meaning that WPM asphalt mastic has better high temperature property than LSM.

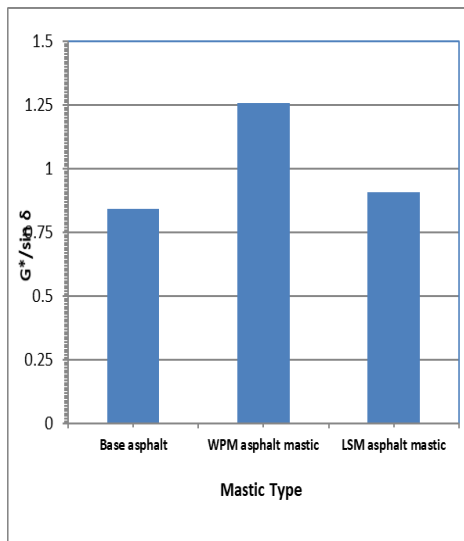


Fig. 6 Rutting parameter of asphalt mastic

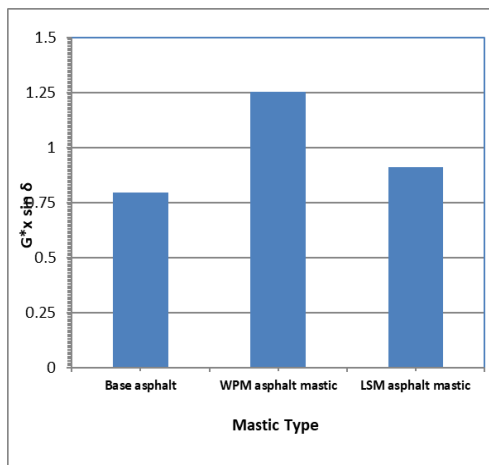


Fig. 7 Fatigue parameter of asphalt mastic

**4.5. Temperature susceptibility**

The penetration index (P.I.) equation (2) [16] were adopted to examine the temperature susceptibility of WPM and LSM mastics.

$$P.I. = \frac{(20 - 500A)}{(1 + 50A)} \tag{2}$$

$$A = \frac{(\log \text{pen.}@T - \log 800)}{(T - R\&B)}$$

Where:

T = Testing temperature

R&B = Softening degree.

Figure 8 shows between the P.I. and mastics. The P.I. values of WPM and LSM mastics are 0.714, and 0.0033, respectively. It can be noticed that both WPM and LSM mastics in the normal range of P.I. (-2.0 to +2.0). This depicts that WPM mastic is less susceptible to temperature varies than LSM.

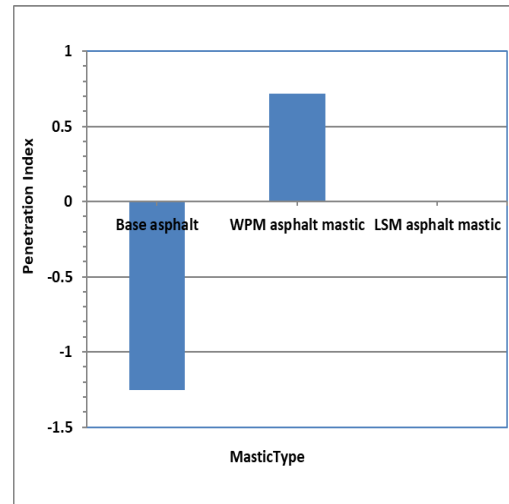


Fig. 8 Penetration index of asphalt mastic

**4.6. Compatibility tests**

The compatibility between WPM, LSM and A40 was examined by passing the binder at the mixing temperature of each binder through a 0.075mm US sieve. It was noticed that the WPM and LSM mastics thus prepared can be stored for future use.

**4.8. Extensional viscosity**

The extensional viscosity ( $\lambda_b$ ) of WPM and LSM mastics in Mpa.s was calculated from equation 5 reported by Al-Hadidy et.al [16, 17].

$$\lambda_b = 3 \times 10^{-6} \{ 1.3 \times 10^{[3 + (R\&B - T_{binder})^{10}]} \} \tag{5}$$

Where:

R&B and  $T_{binder}$  (as defined above).

Table 5 shows  $\lambda_b$  of WPM and LSM mastics. It can be noticed that the  $\lambda_b$  of WPM and LSM at 25°C 15.526 and 6.181 Mpa.s, respectively. Similarly, these values at 60°C were depicted to be  $4.9 \times 10^{-3}$  and  $1.954 \times 10^{-3}$ . This depicts that increasing in temperature leads to decrease in binder  $\lambda_b$ . Furthermore, WPM has a  $\lambda_b$  value higher than LSM.

Table 3: Extensional viscosity of asphalt mastic

Asphalt mastic	$\lambda_b$ , Mpa.S	
	25°C	60°C
A40	1.663	$0.526 \times 10^{-3}$
WPM	15.526	$4.909 \times 10^{-3}$
LSM	6.181	$1.954 \times 10^{-3}$

**4.10. Shear strength**

The cone penetration assay (CPA) was introduced to assess the WPM and LSM shear strength and as shown in Figure 9. 1:1 wt. ratio of A40 binder and WPM/LSM as a filler (100 passing 0.075mm) were: (1) blended at the WPM/LSM

mixing temperature; (2) WPM/LSM: filler was placed into tin vessel and the later was left in laboratory for  $40 \pm 5$  min and then it was cured in water at  $30^\circ\text{C}$  for 60 min; (3) the CPT was applied on the samples with cone weight ( $w$ ) of  $200 \pm 5$  g until the CPA dial reading ( $h$  in dmm) became stable; and (4) the shear stress  $\tau$  (kPa) of WPM/LSM: filler at the inclined cone surface with angle ( $\alpha/2 = 15^\circ$ ) was calculated using equation 6:  $\tau = [981 * w * \cos^2(\alpha/2)] / [3.14 * h^2 * \tan(\alpha/2)]$  (6)

Triplicate samples were tested for each WPM dosage and LMS. Figure 10 depicted that the shear stress of WPM and LSM are 13.48 and 12.56 kPa, respectively. It can be noticed that the shear stress of WPM is better than LSM mastic.

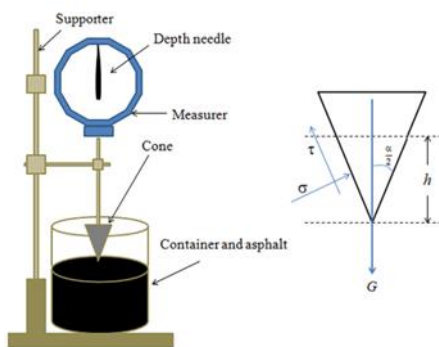


Fig. 9 Shear strength test

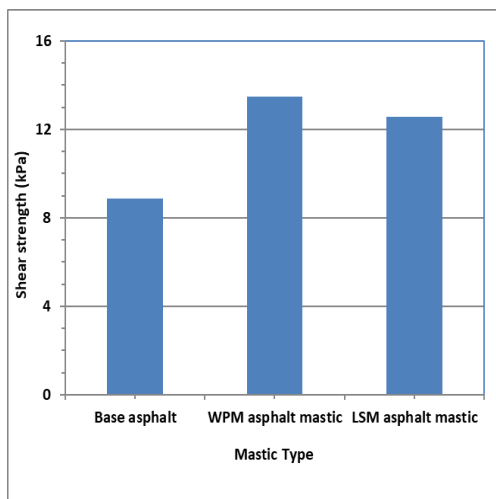


Fig. 10 Shear strength of asphalt mastic

## 5. CONCLUSION

This study used laboratory tests to examine the rheological properties of asphalt mastic with waste powder materials (WPM) as a sustainable filler. One can infer the following conclusions.

1. Compared with LSM, the WPM has porous surface and approximately similar percentage passing #200 sieve, indicating the possibility and feasibility of WPM as filler obtained from the polishing of mosaic tiles to improve the performance of asphalt. In addition, the physical adsorption between the WPM filler and asphalt is the main mode of action.
2. The WPM has a greater impact than the LSM in raising the shear strength of asphalt binder. Filler in asphalt mastic can absorb and stabilize asphalt (particularly light components), as well as improve viscosity and rigidity.
3. Although WPM has a greater impact on high temperatures ( $G^*/\sin \delta$ ) and the characteristics of asphalt mastic, it greatly outperformed LMF when added.
4. WPM and LSM can effectively improve the high temperature sensitivity of asphalt binder, and WPM is the better one.
5. WPM exhibited lower penetration, ductility, and elastic recovery at  $25^\circ\text{C}$ , and higher softening points than LSM. Furthermore, WPM exhibited similar mixing and compaction temperatures to those for LSM.
6. The  $\lambda_b$  of WPM at  $25^\circ\text{C}$  and  $60^\circ\text{C}$  was found to be higher than that for LSM.

## REFERENCES

- [1] I. Boustead, *Eco-profiles of the European polymer industry. Report 3. Polythene and polypropylene*. Association of Plastics Manufacturers in Europe, 1993.
- [2] A. Al-Hadidy, "Sustainable recycling of sulfur waste through utilization in asphalt paving applications," *International Journal of Pavement Research and Technology*, pp. 1–13, 2022, <https://doi.org/10.1007/s42947-021-00143-w>.
- [3] Y. Xiaokai, X. Rui, F. Tianqi, Y. Taoand and S. Yanping, "Laboratory investigation of the rheological property of activated coal gangue modified asphalt binder," *Mater. Rev.* vol. 12, pp. 135–139, 2015.
- [4] P. K. Gautam, P. Kalla, A. S. Jethoo, R. Agrawal, and H. Singh, "Sustainable use of waste in flexible

- pavement: A review," *Construction and Building Materials*, vol. 180, pp. 239–253, 2018.
- [5] M. R. Pouranian and M. Shishebor, "Sustainability assessment of green asphalt mixtures: A review," *Environments*, vol. 6, no. 6, p. 73, 2019.
- [6] J. Wang, J. Yuan, F. Xiao, Z. Li, J. Wang, and Z. Xu, "Performance investigation and sustainability evaluation of multiple-polymer asphalt mixtures in airfield pavement," *Journal of Cleaner Production*, vol. 189, pp. 67–77, 2018.
- [7] R. Xiong *et al.*, "Experimental Investigation on Related Properties of Asphalt Mastic with Activated Coal Gangue as Alternative Filler," *International Journal of Pavement Research and Technology*, Mar. 2018, doi: 10.1016/j.ijprt.2018.03.002.
- [8] V. Punith and A. Veeraragavan, "Behavior of asphalt concrete mixtures with reclaimed polyethylene as additive," *Journal of materials in civil engineering*, vol. 19, no. 6, pp. 500–507, 2007.
- [9] S. Colagrande, "Polyolefinic plastics taken from solid urban waste in bituminous concrete," In *Cabrera JG, editor. Proceedings of the Second European Symposium on Performance and Durability of Bituminous Materials*, University of Leeds, Leeds, 1997, p.85-100.
- [10] S. K. Rasheed and A. Al-Hadidy, "Evaluation of Sulfur Waste as Sustainable Mineral Filler in Asphalt Paving Mixtures," *International Journal of Pavement Research and Technology*, pp. 1–14, 2022, doi:https://doi.org/10.1007/s42947-022-00229-z.
- [11] R. Xiong, J. Fang, A. Xu, B. Guan, and Z. Liu, "Laboratory investigation on the brucite fiber reinforced asphalt binder and asphalt concrete," *Construction and Building Materials*, vol. 83, pp. 44–52, 2015.
- [12] ASTM Standard Specifications, (2015). Part IB, Volume 04.03 Road and Paving Materials Vehicle Pavement Systems.
- [13] State cooperation of road and bridges (SCRB), "Hot mix asphaltic concrete pavement," *Iraqi standard specification*, Ministry of Housing and Construction. Department of Design and Study, Section R-9, 1999.
- [14] National Center for Construction Laboratories (NCCL), "Materials and Construction Works Specification", Ministry of Housing and Construction and Public Works. Directorate of Research and Technical Affairs, January, 2018, Baghdad-Iraq.
- [15] American society for Testing and Materials (ASTM), "Standard Test Method for Determining the Rheological Properties of Asphalt Binder Using a Dynamic Shear Rheometer", D7175, 2015 Edition.
- [16] A.-R. I. Al-Hadidy, Z. A. Al-Kazzaz, and A. A. M. Ali, "Deterministic Extensional Viscosity and Cracking Index of Polypropylene-Modified-Asphalt Binder," *Tikrit Journal of Engineering Sciences*, vol. 27, no. 1, pp. 25–29, 2020.
- [17] A. Al-Hadidy, "Engineering behavior of aged polypropylene-modified asphalt pavements," *Construction and Building Materials*, vol. 191, pp. 187–192, 2018.

## التحري المختبري للخصائص الريولوجية للأسفلت ماستك الحاوي على مخلفات الطحن الناتجة من عملية جلي الكاشي الموزائيك كمادة مائنة

تان اي-جيو\*\*  
tanyiqiu@163.com

محمد غاتم جميل\*  
mohammed\_g72@uomosul.edu.iq

عبد الرحيم ابراهيم الحديدي\*  
alhadidy@uomosul.edu.iq

وانك جيانى\*\*  
wangjiani@hit.edu.cn

دونك زيچياو\*\*  
hitdzj@hit.edu.cn

\* جامعة الموصل - كلية الهندسة - قسم الهندسة المدنية - موصل - العراق  
\*\* علوم النقل والهندسة - معهد هار بين للتكنولوجيا- الصين

تاريخ القبول: 2023-02-26

استلم بصيغته المنقحة: 2023-02-16

تاريخ الاستلام: 2023-01-12

### المخلص

لتقييم إمكانية استخدام مخلفات مواد الطحن من جلي الكاشي الموزائيك كمادة مائنة في المزجات الاسفلتية، بعض خصائص الأسفلت ماستك الحاوي على هذه المخلفات تم التحري عنها في هذه الدراسة، ومقارنتها مع مادة كاربونات الكالسيوم. الأسفلت ماستك المنتج احتوى على نسبة وزنية 1:1 (اسفلت: مادة مائنة). الخصائص الريولوجية تم اختبارها عن طريق النفاذية، نقطة اللبونة، الأستطالة، الرجوعي، لزوجة فورل، اللزوجة الفاتقة، القص الريولوجي، تأثير الحرارة، التجانس و مخروط النفاذية. أوضحت النتائج إمكانية استخدام مخلفات كاشي الموزائيك كمادة مائنة لتحسين كفاءة الأسفلت من حيث مقاومة القص، التشوهات الدائمية والكلل بالإضافة الى مقاومة التغيرات بالحرارة مقارنة بكاربونات الكالسيوم.

الكلمات الداله:

الخصائص الريولوجية، مخلفات مادة طحن كاشي الموزائيك، كاربونات الكالسيوم.